

# Petroleum and natural gas industries — Induction bends, fittings and flanges for pipeline transportation systems —

## Part 2: Fittings

The European Standard EN 14870-2:2004 has the status of a  
British Standard

ICS 23.040.40; 75.200

## National foreword

This British Standard is the official English language version of EN 14870-2:2004.

The UK participation in its preparation was entrusted by Technical Committee PSE/17, Materials and equipment for petroleum, petrochemical and natural gas industries, to Subcommittee PSE/17/2, Transmission pipelines, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

### Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

**Compliance with a British Standard does not of itself confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 20 January 2005

### Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 34, an inside back cover and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

### Amendments issued since publication

Amd. No.	Date	Comments

© BSI 20 January 2005

ISBN 0 580 45313 8

---

ICS 23.040.40; 75.200

English version

**Petroleum and natural gas industries - Induction bends, fittings and flanges for pipeline transportation systems - Part 2: Fittings (ISO 15590-2:2003 modified)**

Industries du pétrole et du gaz naturel - Coudes d'induction, raccords et brides pour systèmes de transport par conduites - Partie 2 : Raccords (ISO 15590-2:2003 modifiée)

Erdöl- und Erdgasindustrie - Im Induktionsverfahren hergestellte Rohrbögen, Fittings und Flansche für Rohrleitungstransportsysteme - Teil 2: Fittings (ISO 15590-2:2003 modifiziert)

This European Standard was approved by CEN on 30 September 2004.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**Management Centre: rue de Stassart, 36 B-1050 Brussels**

## Contents

	page
Explanatory Note .....	3
Foreword.....	4
Introduction .....	5
1 Scope .....	6
2 Normative references .....	6
3 Terms and definitions .....	8
4 Symbols and abbreviated terms .....	8
5 Designation .....	10
6 Pressure rating and design .....	10
6.1 General.....	10
6.2 Tees and headers.....	10
6.3 Extruded outlet headers.....	10
7 Information to be supplied by the purchaser .....	11
7.1 Principal information.....	11
7.2 Supplementary information .....	11
8 Manufacturing .....	12
8.1 Manufacturing procedure specification .....	12
8.2 Starting material.....	13
8.3 Fitting manufacture .....	13
9 Testing and inspection.....	15
9.1 General requirements.....	15
9.2 Extent of testing and inspection .....	15
9.3 Chemical composition .....	17
9.4 Mechanical testing.....	17
9.5 Non-destructive testing.....	23
9.6 Dimensions.....	25
9.7 Gauging .....	25
9.8 Hydrostatic testing .....	25
10 Inspection document.....	25
11 Marking .....	25
Annex A (normative) Design calculations.....	27
Annex B (normative) Proof test.....	30
Annex ZA (normative) Normative references to international publications with their corresponding European publications .....	33
Bibliography .....	34

## Explanatory Note

ISO 15590-2:2003, developed within ISO/TC 67 SC 2, has been taken over as a European Standard EN 14870-2 (ISO 15590-2:2003 modified).

The scope of ISO/TC 67/SC 2 is pipeline transportation systems for the petroleum and natural gas industries without exclusions. However in CEN, the scopes of CEN/TC 12 and CEN/TC 234 overlapped until 1995. This scope overlap caused problems for the parallel procedure for the above-mentioned items. The conflict in scope was resolved when both the CEN/Technical Committees and the CEN/BT took the following resolution:

**Resolution BT 38/1995:**

**Subject: Revised scope of CEN/TC 12**

***“BT endorses the conclusions of the coordination meeting between CEN/TC 12 “Materials, equipment and offshore structures for petroleum and natural gas industries” and CEN/TC 234 “Gas supply” and modifies the CEN/TC 12 scope, to read:***

***“Standardization of the materials, equipment and offshore structures used in drilling, production, refining and the transport by pipelines of petroleum and natural gas, excluding on-land supply systems used by the gas supply industry and those aspects of offshore structures covered by IMO requirement (ISO/TC 8).***

***The standardization is to be achieved wherever possible by the adoption of ISO Standards.”***

Resulting from Resolution BT 38/1995, "**gas supply on land**" has been excluded from the scope of ISO 15590-2:2003 for the European adoption by CEN/TC 12.

Equivalence with European Standards is provided in Annex ZA.

## Foreword

The text of ISO 15590-2:2003 has been prepared by Technical Committee ISO/TC 67 "Materials, equipment and offshore structures for petroleum, petrochemical and natural gas industries" of the International Organization for Standardization (ISO) and has been taken over as EN 14870-2:2004 by Technical Committee CEN/TC 12 "Materials, equipment and offshore structures for petroleum, petrochemical and natural gas industries", the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2005, and conflicting national standards shall be withdrawn at the latest by June 2005.

This document includes a Bibliography.

International Standard ISO 15590-2 was prepared by Technical Committee ISO/TC 67, Materials, equipment and offshore structures for petroleum, petrochemical and natural gas industries, Subcommittee SC2, Pipeline transportation systems.

EN 14870 consists of the following parts, under the general title *Petroleum and natural gas industries — Induction bends, fittings and flanges for pipeline transportation systems*:

— *Part 1: Induction bends (ISO 15590-1:2001 modified)*

— *Part 2: Fittings (ISO 15590-2:2003 modified)*

The following part is under preparation:

— *Part 3: Flanges*

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

## Introduction

Users of this document should be aware that further or differing requirements may be needed for individual applications. This document is not intended to inhibit a manufacturer from offering, or the purchaser from accepting, alternative equipment or engineering solutions for the individual application. This can be particularly applicable where there is innovative or developing technology. Where an alternative is offered, the manufacturer should identify any variations from this document and provide details.

## 1 Scope

This document specifies the technical delivery conditions for unalloyed or low-alloy steel seamless and welded pipeline fittings for use in pipeline transportation systems for the petroleum and natural gas industries as defined in EN 14161.

This document is applicable to welding-end fittings such as elbows, caps, tees, single or multiple extruded headers, reducers, and transition sections made from seamless and welded pipe of unalloyed or low-alloy steels.

This document specifies three classes of fitting corresponding to increasing quality requirements in accordance with the technical delivery conditions of ISO 3183 for pipe as indicated in Table 1.

**Table 1 — Fitting class and corresponding pipe standard**

Fitting class	Corresponding pipe standard
Class A	ISO 3183-1
Class B	ISO 3183-2
Class C	ISO 3183-3

This document is not applicable to the selection of the fitting class.

This document is not applicable to the materials for, or the attachment of, factory-welded extensions.

On-land supply systems used by the gas supply industry are excluded from the scope of this document.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 287-1, *Qualification test of welders — Fusion welding — Part 1: Steels.*

EN 14161, *Petroleum and natural gas industries - Pipeline transportation systems (ISO 13623:2000 modified).*

EN ISO 377:1997, *Steel and steel products - Location and preparation of samples and test pieces for mechanical testing (ISO 377:1997).*

EN ISO 2566-1, *Steel - Conversion of elongation values - Part 1: Carbon and low alloy steels (ISO 2566-1:1984).*

EN ISO 6507-1, *Metallic materials - Vickers hardness test - Part 1: Test method (ISO 6507-1:1997).*

EN ISO 7438, *Metallic materials - Bend test (ISO 7438:1985).*

EN ISO 15156-2:2003, *Petroleum, petrochemical and natural gas industries - Materials for use in H<sub>2</sub>S-containing environments in oil and gas production - Part 2: Cracking-resistant carbon and low alloy steels, and the use of cast irons (ISO 15156-2:2003).*

EN ISO 15614-1, *Specification and qualification of welding procedures for metallic materials - Welding procedure test - Part 1: Arc and gas welding of steels and arc welding of nickel and nickel alloys (ISO 15614-1:2004).*

ISO 148, *Steel — Charpy impact test (V-notch).*

ISO 148-2, *Metallic materials — Charpy pendulum impact test — Part 2: Verification of test machines.*



ISO 148-3, *Metallic materials — Charpy pendulum impact test — Part 3: Preparation and characterization of Charpy V reference test pieces for verification of test machines.*

ISO 783, *Metallic materials — Tensile testing at elevated temperature.*

ISO 3183-1, *Petroleum and natural gas industries — Steel pipe for pipelines — Technical delivery conditions — Part 1: Pipes of requirement class A.*

ISO 3183-2, *Petroleum and natural gas industries — Steel pipe for pipelines — Technical delivery conditions — Part 2: Pipes of requirement class B.*

ISO 3183-3, *Petroleum and natural gas industries — Steel pipe for pipelines — Technical delivery conditions — Part 3: Pipes of requirement class C.*

ISO 3834-2, *Quality requirements for welding — Fusion welding of metallic materials — Part 2: Comprehensive quality requirements.*

ISO 4885:1996, *Ferrous products — Heat treatments — Vocabulary.*

ISO 6892, *Metallic materials — Tensile testing at ambient temperature.*

ISO/TR 7705:1991, *Guidelines for specifying Charpy V-notch impact prescriptions in steel specifications.*

ISO 9712, *Non-destructive testing — Qualification and certification of personnel.*

ISO 10474, *Steel and steel products — Inspection documents.*

ISO 11496, *Seamless and welded steel tubes for pressure purposes — Ultrasonic testing of tube ends for the detection of laminar imperfections.*

ISO 12095, *Seamless and welded steel tubes for pressure purposes — Liquid penetrant testing.*

ISO 12096, *Submerged arc-welded steel tubes for pressure purposes — Radiographic testing of the weld seam for the detection of imperfections.*

ISO 13664, *Seamless and welded steel tubes for pressure purposes — Magnetic particle inspection of the tube ends for the detection of laminar imperfections.*

ASME<sup>1)</sup> B16.9, *Factory-made wrought butt welding fittings.*

ASME B31.8, *Gas transmission and distribution piping systems.*

ASME IX, *Boiler and pressure vessel code, Section IX — Welding and brazing procedures, welders, brazers, and welding and brazing operators.*

ASTM<sup>2)</sup> E 112, *Standard test methods for determining average grain size.*

ASTM E 709, *Standard guide for magnetic particle examination.*

MSS<sup>3)</sup> SP-75, *Specification for high test wrought butt welding fittings.*

---

1) American Society of Mechanical Engineers, 345 East 47<sup>th</sup> Street, NY 10017-2392, USA.

2) American Society for Testing and Materials, 100 Bar Harbor Drive, West Conshohocken, PA 19428-2959, USA.

3) Manufacturers Standardization Society of the Valve & Fittings Industry, 127 Park Street, N.E., Vienna, Virginia 22180, USA.

### 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 4885:1996 and the following apply.

#### 3.1 by agreement

agreed between manufacturer and purchaser

[EN 14870-1:2004]

#### 3.2 extrados

outer curved section of the elbow

NOTE Adapted from EN 14870-1:2004.

#### 3.3 heat, noun

batch of steel prepared in one steel-making process

NOTE Adapted from EN 14870-1:2004.

#### 3.4 intrados

inner curved section of the elbow

NOTE Adapted from EN 14870-1:2004.

#### 3.5 manufacturing procedure specification MPS

document which specifies the process control parameters and the acceptance criteria to be applied for all manufacturing, inspection and testing activities performed during fitting manufacture

#### 3.6 tangent

straight section at the ends of the fitting

NOTE Adapted from EN 14870-1:2004.

#### 3.7 test unit

fitting or test piece of the same designation, starting material wall thickness, heat, manufacturing procedure specification, and heat treatment condition

### 4 Symbols and abbreviated terms

$A_0$	original cross-sectional area of the parallel length of a tensile test specimen
$D$	outside diameter
$D_p$	specified outside diameter of matching pipe
$D_n$	minor outside diameter of a conical reducer or reducing tee at any point, $n$ , under consideration, measured perpendicular to the longitudinal axis
$E$	factor used to calculate $t_1$ (see A.1)

$f$	factor used to calculate proof test pressure (see Table B.1)
$P_{cm}$	crack measurement parameter (see Table 4)
$p$	design pressure
$p_p$	numerical value of the computed proof pressure
$R_m$	tensile strength
$R_{m, red}$	allowable tensile strength of a reducer
$R_{t0,5}$	yield strength for 0,5 % total elongation
$R_{smys}$	specified minimum yield strength
$T_{d, min}$	minimum design temperature specified by the purchaser
$t$	nominal wall thickness
$t_D$	wall thickness of thicker component for joints of unequal thickness (see Figure 1)
$t_i$	minimum wall thickness required in the intrados
$t_p$	nominal wall thickness of matching pipe
$t_n$	specified wall thickness of reducers and reducing tees at diameter $D_n$
$\alpha$	included angle of a conical reducer
$\rho_0$	radius of curvature of the external contoured portion of the outlet of a tee
CE	carbon equivalent (see Table 4)
CTOD	crack tip opening displacement
DN	nominal size
HIC	hydrogen-induced cracking
MT	magnetic particle testing
NDT	non-destructive testing
PT	liquid penetrant testing
RT	radiographic testing
SMYS	specified minimum yield strength
SSC	sulfide stress-cracking
UT	ultrasonic testing

## **5 Designation**

Designation of fittings shall take the form:

**EN 14870-2 YY xxx-Z,**

where

- YY is a textual description of the type of fitting, corresponding to one of the following: EL for elbow, TE for tee, CA for cap, CR for concentric reducer, ER for eccentric reducer and NR for conical reducer, preceded by the size designation (e.g. "DN 600 EL" is a DN 600 elbow);
- xxx is the specified minimum yield strength requirement in MPa;
- Z is the suffix A or B or C, to identify the fitting class for use in non-sour service, or the suffix CS to identify class C fittings for use in sour-service conditions.

## **6 Pressure rating and design**

### **6.1 General**

The capability of the fitting to withstand internal pressure shall equal or exceed that of the matching pipe. The verification of the capability shall be made by calculation and/or proof testing. The calculations shall be made in accordance with Annex A. The proof test procedure shall be as defined in Annex B. Additional requirements on strength design verifications, such as resistance to internal pressure under special load cases in accordance with EN 14161, shall be indicated at the time of enquiry or order.

The design calculations and/or results of proof testing shall be available for review at the manufacturer's facility.

If the SMYS of the fitting material is less than that of the matching pipe, the minimum thickness of the fitting end shall be increased such that the product of its thickness times its SMYS shall at least equal the product of the specified wall thickness and the SMYS of the matching pipe, in accordance with MSS SP-75.

### **6.2 Tees and headers**

Outlet branches in tees and headers manufactured from seam-welded pipe shall be positioned diametrically opposite the longitudinal weld. When this positioning is not possible, the location shall be decided by agreement.

The design and welding for the attachment of guide bars of barred tees shall be decided by agreement prior to manufacture of the tee.

### **6.3 Extruded outlet headers**

Extruded outlet headers shall be designed to comply with ASME B31.8.

## 7 Information to be supplied by the purchaser

### 7.1 Principal information

The purchaser shall provide the following information in the order given below:

- a) fitting designation;
- b) required fitting dimensions, including:
  - 1) nominal outside diameters;
  - 2) minimum wall thicknesses at the welding ends;
  - 3) radius and type of radius (e.g. long-radius);
  - 4) the angle (for elbows);

NOTE Guidance on specific dimensions to specify is given in ISO 3545-3.

- c) end-preparation details;
- d) whether the purchaser wishes to approve the MPS prior to commencement of manufacturing.

### 7.2 Supplementary information

If applicable, the purchaser shall specify the following supplementary information:

- a) minimum design temperature;
- b) maximum design temperature;
- c) maximum wall thickness;
- d) special dimensional requirements;
- e) requirements for supplementary inspection and testing;
- f) requirements for gauging and other measurements of dimensions where different from this document;
- g) pipeline design standard or design factors if different from EN 14161;
- h) pipeline operating conditions;
- i) mechanical property requirements at the maximum design temperature;
- j) requirements for proof, burst, or hydrostatic testing;
- k) activities for witnessing and approval by purchaser;
- l) coating or painting requirements;
- m) marking requirements where different from this document;
- n) packaging and shipping instructions;
- o) third-party inspection organization;

- p) ISO 10474 standard designation of inspection document required;
- q) requirements for format and additional content of the inspection document;
- r) whether testing of welding procedures, welders, or welding operators specific to the order is required;
- s) whether approval of the MPS is to be by review of previous production data or by testing;
- t) PWHT (see 9.1);
- u) HIC testing (see 9.4.7);
- v) SCC testing (see 9.4.8).

## **8 Manufacturing**

### **8.1 Manufacturing procedure specification**

Fittings shall be manufactured in accordance with a documented MPS. If specified by the purchaser, manufacturing shall not proceed until the MPS has been accepted by the purchaser.

The MPS shall specify the following items:

- a) for the starting material:
  - 1) name of manufacturer;
  - 2) steel-making process;
  - 3) steel grade;
  - 4) product form and dimensions;
  - 5) chemical composition, including that of the weld seam;
  - 6) welding procedure specification;
- b) for fitting manufacture:
  - 1) forming procedure;
  - 2) welding procedure specification and approval record;
  - 3) heat treatment procedure including thermal cycles;
  - 4) machining requirements;
  - 5) inspection and test requirements;
  - 6) traceability;
- c) additional requirements such as end preparation, coating, and marking.

An approval of the MPS may be required, either by review of the manufacturer's previous production data or by performance of the mandatory tests listed in Table 2, at the beginning of production.

## 8.2 Starting material

The starting material for forming into fittings shall be blooms, billets, slabs, forging quality bar, plate, fusion-welded with filler metal or seamless tubular products, produced from fully-killed steels.

High-frequency welded (HFW) and helical-seam submerged-arc welding (SAWH) pipes shall not be used.

## 8.3 Fitting manufacture

### 8.3.1 Forming

All forming operations shall be performed in accordance with the MPS.

### 8.3.2 Welding

Welding operations shall be conducted in accordance with those elements of ISO 3834-2 decided by agreement and the requirements of this document.

Welding and repair welding shall be performed in accordance with procedures qualified in accordance with ASME IX or EN ISO 15614-1. Welders and welding operators shall be qualified in accordance with ASME IX or EN 287-1.

Acceptance criteria for all tests shall be as specified in Clause 9.

Where practicable, longitudinal butt welds should be double-sided. Backing rings shall not be used. All welds shall have complete penetration and shall be finished in accordance with Clause 9.

Temporary welded attachments shall be removed, where possible, before heat treatment and the weld area shall be treated in accordance with 9.5.3.4 and 9.5.3.5.

Fittings shall not contain girth welds.

All welds that will remain in the fitting shall be heat-treated in accordance with 8.3.3.

### 8.3.3 Heat treatment

All fittings shall be normalized, normalized and tempered, or quenched and tempered after welding and/or forming. The heat treatment shall be performed in accordance with a documented procedure. The procedure shall define the following parameters, where appropriate, for the type of heat treatment:

- a) heating schedule;
- b) soaking temperature;
- c) soaking time;
- d) cooling schedule;
- e) quenching temperature;
- f) quenching medium, including commencing and final medium temperature.


A record shall be maintained of each heat treatment. When submission of the heat treatment record is specified, it shall be included in the inspection document.

The tolerances on specified nominal values of soaking temperature and soaking time shall be  $\pm 15$  °C and + 20 %, respectively.


8.3.4 End preparation

For unequal wall thicknesses, the joint design shall be as shown in Figure 1.

Dimensions in millimetres

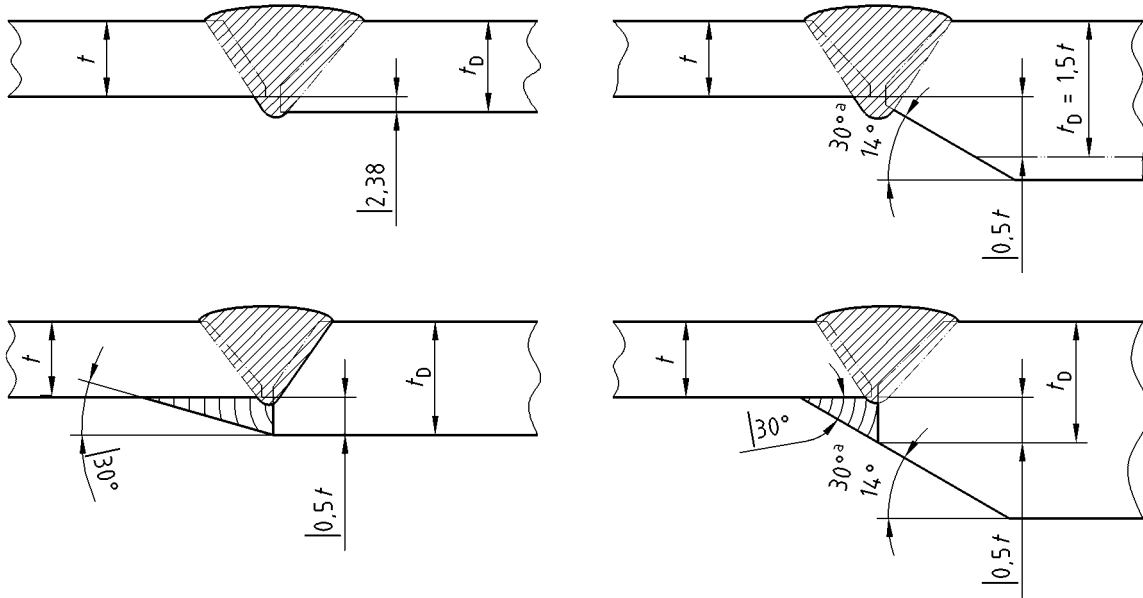


a) Internal offset

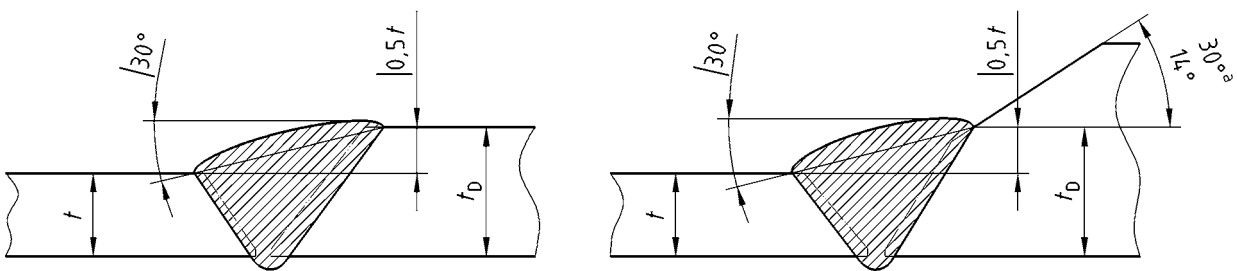

b) External offset



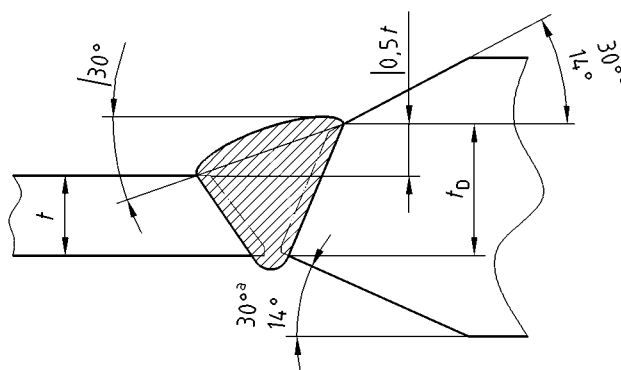

c) Combination

**Key**

If the SMYSs of the sections to be joined are not equal, the minimum thickness,  $t_D$ , shall be not less than  $t$  times the ratio of the SMYS of the pipe and fitting, but shall not exceed  $1,5t$ .

<sup>a</sup> There is no restriction on the minimum angle if the materials joined have equal SMYS.

**Figure 1 — Bevel designs for unequal wall thicknesses****9 Testing and inspection****9.1 General requirements**

Testing and inspection shall be carried out on fittings after final heat treatment.

If the pipeline installation techniques will require post-weld heat treatment (PWHT) of the fitting, additional testing may be requested to demonstrate that the mechanical properties of the fitting are also achieved after PWHT. Details of the PWHT thermal cycle to be used during pipeline installation shall be specified. The test requirements and acceptance criteria shall be by agreement.

Where the procedure requirements of 8.3.3 are not met, test pieces shall be taken from each heat treatment batch.

**9.2 Extent of testing and inspection**

The testing and inspection to be performed during qualification and production shall be as summarized in Table 2 for each fitting class.

Production testing shall be performed at the minimum frequency specified in Table 3.

Test pieces for mechanical testing shall be taken from one or more of the following:

- extension lengths, formed and heat-treated as part of the fitting and/or test piece attached to the fitting;
- starting material which has been subjected to the same forging reduction and heat treatment as the proposed fitting;
- a fitting.

Locations for the test pieces to be taken from a fitting shall be established by agreement. The sample of starting material shall be heat-treated with or as part of the fittings in the same heat treatment batch in accordance with EN ISO 377:1997, Clause 5.

Fittings heat-treated within the tolerance requirements of 8.3.3 may be considered as being in the same heat treatment condition.

**Table 2 — Summary of testing and inspection requirements**

	Test	Class A	Class B	Class C	Clause number specifying acceptance criteria
Chemical analysis	Chemical composition	M	M	M	9.3
Physical tests	Tensile – base metal	M	M	M	9.4.2.3
	Transverse weld tensile	M <sup>a</sup>	M <sup>a</sup>	M <sup>a</sup>	9.4.2.3
	Impact – fitting body	O	M	M	9.4.3.3
	Impact – weld seam	O	M	M	9.4.3.3
	Through-thickness hardness	O	M	M	9.4.4.2
	Surface hardness	O	O	O	9.4.5
	Metallography	Q	Q	Q <sup>b</sup>	9.4.6.2
	HIC	N	N	O <sup>c,d</sup>	9.4.7
	SSC	N	N	O <sup>c,d</sup>	9.4.8
	CTOD	N	N	O	9.4.9
	Guided bend (weld seam)	Q	Q	Q	9.4.10.3
NDT	Visual inspection	M	M	M	9.5.3
	End preparation (MT or PT)	M	M	M	9.5.4
	Fitting end (UT)	N	M	M	9.5.4
	Weld seam (RT or UT) <sup>d</sup>	M	M	M	9.5.5
	Fitting body (UT or MT) <sup>e</sup>	O	O	O	9.5.7
	Residual magnetism	O	M	M	9.5.8
Dimensions	Wall thickness	M	M	M	9.6
	Inside diameter at ends	M	M	M	9.6
	Out-of-roundness at ends	M	M	M	9.6
	Specific dimensions	M	M	M	9.6

NOTE The abbreviations mean as follows:  
M = Requirement mandatory in production;  
N = Not required;  
O = Requirement for test or inspection at the purchaser's option;  
Q = Required for approval of the welding procedure only, otherwise at the purchaser's option.

<sup>a</sup> May be omitted for fittings with  $D < 210$  mm.  
<sup>b</sup> Production test which shall be performed for fittings intended for sour service.  
<sup>c</sup> Option need not be considered for fittings intended for non-sour service. If applied, this testing may be performed as part of the MPS qualification testing.  
<sup>d</sup> May be carried out on the starting material by agreement.  
<sup>e</sup> By agreement.

Table 3 — Extent of testing and inspection

Type of test	Number of tests
Chemical composition	One per heat
Tensile — base metal	One per test unit
Transverse weld tensile	One per test unit
Impact — base metal	One set per test unit
Impact — weld seam	37 mm thickness and above: two sets per test unit less than 37 mm: 1 set per test unit
Through-thickness hardness	One per test unit
Surface hardness	By agreement
Metallography	By agreement
HIC	By agreement
SSC	By agreement
CTOD	By agreement
Guided bend (weld seam)	Two per qualification test
NDT	Every fitting <sup>a</sup>
Dimensional inspection	Every fitting

<sup>a</sup> Except for determining residual magnetism, which shall be at a frequency to be established by agreement for fittings demagnetized during production, otherwise 25 % of the fittings shall be selected at random.

### 9.3 Chemical composition

The product analysis shall be in accordance with Table 4.

### 9.4 Mechanical testing

#### 9.4.1 Preparation of test pieces

Test pieces shall be prepared in accordance with EN ISO 377.

#### 9.4.2 Tensile testing

##### 9.4.2.1 Test pieces

Orientation of the base metal test pieces shall be as follows:

- transverse to the major axis of the fitting for  $D \geq 210$  mm;
- longitudinal to the major axis of the fitting for  $D < 210$  mm.

Transverse test pieces shall be cold-flattened. Round bar made from a test piece may be used. Round-bar test pieces machined from unflattened samples may be used by agreement.

Welds shall be ground flush. Local imperfections and mill scale shall be removed.

9.4.2.2 Test method

Tensile testing at ambient temperature shall be carried out in accordance with ISO 6892. If specified, tensile testing at elevated temperatures shall be carried out in accordance with ISO 783. The frequency and acceptance criteria shall be by agreement.

For base metal,  $R_{t0,5}$ ,  $R_m$ , and percentage elongation after fracture shall be determined. For tensile tests transverse to the weld, it is required only to determine  $R_m$ .

The percentage elongation after fracture shall be reported with reference to a gauge length of  $5,65\sqrt{A_0}$ . If other gauge lengths are used, the elongation referred to a gauge length of  $5,65\sqrt{A_0}$  shall be determined in accordance with EN ISO 2566-1.

9.4.2.3 Requirements

The tensile properties shall meet the requirements of the corresponding part of ISO 3183.

Table 4 — Chemical composition for product analyses

Element	Maximum permitted alloy content, mass fraction, %		
	Class A	Classes B and C	Class CS
C	0,20	0,18	0,18
Mn	1,60	1,60	1,30
Si	0,40	0,40	0,40
P	0,025	0,025	0,025
S	0,010	0,010	0,003 <sup>a</sup>
V	0,10	0,10	0,10
Nb	0,05	0,05	0,05
Ti	0,04	0,04	0,04
Cr	0,25	0,25	0,25
Mo	0,10	0,10	0,10
Ni	0,50	0,50	0,50
Cu	0,35	0,35	0,35
Al	0,05	0,05	0,05
N	0,012	0,012	0,012
B	0,000 5	0,000 5	0,000 5
Ca <sup>a</sup>	0,006	0,006	0,006
CE <sup>b</sup>	0,45	0,43	0,43
$P_{cm}$ <sup>c</sup>	0,23	0,21	0,21

V + Nb + Ti shall not exceed 0,15 %.

Cr + Mo + Ni + Cu shall not exceed 0,6 %. Higher Cr, Mo and Ni content may be acceptable by agreement, where required for special applications such as low temperatures and/or thick sections.

The total Al:N ratio shall not be less than 2:1.

<sup>a</sup> Ca:S ratio shall be a minimum of one (1) for S in the range 0,001 5 % to 0,003 0 %.

<sup>b</sup> Carbon equivalent, calculated as follows:

$$CE = C + \frac{Mn}{6} + \frac{Cr + Mo + V}{5} + \frac{Ni + Cu}{15}$$

<sup>c</sup> Crack measurement parameter, calculated as follows:

$$P_{cm} = C + \frac{Si}{30} + \frac{Ni}{60} + \frac{V}{10} + \frac{Mo}{15} + \frac{Cr + Mn + Cu}{20} + 5B$$

### 9.4.3 Charpy V-notch impact testing

#### 9.4.3.1 Test pieces


Charpy V-notch test pieces shall be prepared in accordance with ISO 148, ISO 148-2 and 148-3, with the axis of the notch perpendicular to the fitting surface.

The orientation and size of the test pieces shall be transverse with the greatest possible width between 5 mm and 10 mm. If transverse test pieces with a minimum width of 5 mm are not possible, longitudinal test pieces with the greatest possible width between 5 mm and 10 mm shall be used.

Impact testing is not required if the fitting dimensions are insufficient to extract longitudinal base metal test pieces with a minimum width of 5 mm.

Charpy V-notch test pieces shall be taken from the sample in accordance with ISO 3183-3.

Test pieces for welds shall be taken from the weld centreline. Test pieces of the fusion line should be taken by agreement, in which case the notch location shall be as shown in Figure 2.

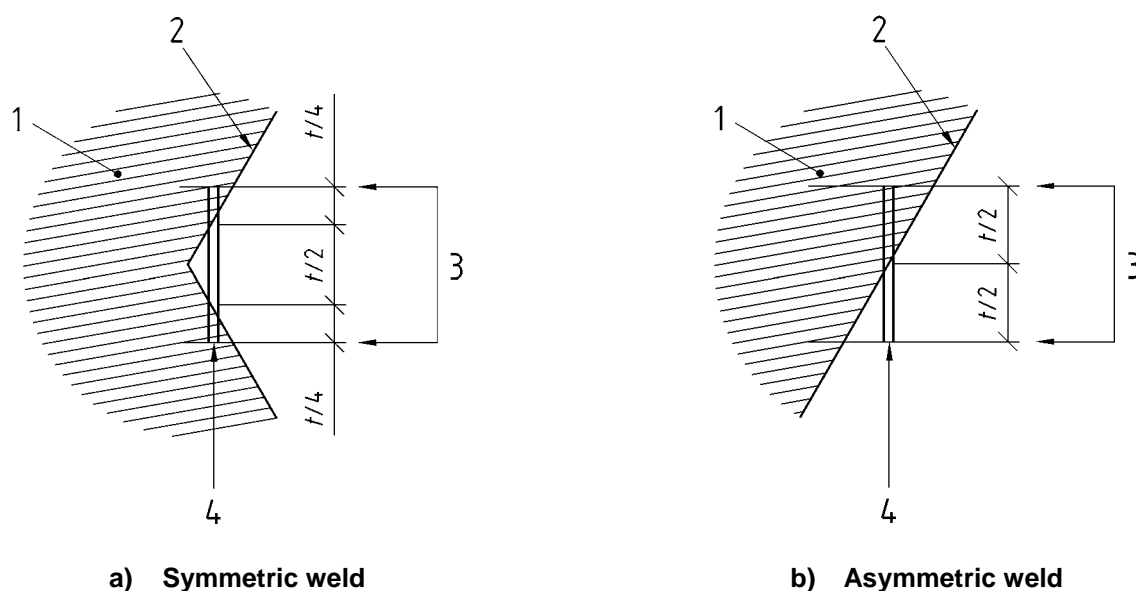

#### Key

- 1 Weld
- 2 Fusion line
- 3 Test piece edges
- 4 Charpy notch
- $t$  is the length of Charpy V-notch

Figure 2 — Location of Charpy V-notch in weld fusion lines

#### 9.4.3.2 Test method

Each set of impact tests shall consist of three adjacent test pieces taken from a single, non-flattened sample.

Charpy V-notch impact testing shall be in accordance with ISO 148, ISO 148-2 and ISO 148-3. An additional requirement to report shear area of the fracture surface shall be by agreement.

The impact test temperature shall be established in accordance with Table 5.

Table 5 — Maximum Charpy V-notch test temperature

Nominal wall thickness mm	Test temperature °C		
	Class A	Class B	Class C
$t \leq 20$	By agreement	$T_{d, \min}$	$T_{d, \min} - 10$
$20 < t \leq 25$	By agreement	$T_{d, \min}$	$T_{d, \min} - 20$
$t > 25$	By agreement	By agreement	By agreement
In no case shall the test temperature exceed 0 °C.			

### 9.4.3.3 Requirements

The results of the Charpy V-notch impact tests shall meet the following requirements:

- a) for each set of tests, the minimum average absorbed energy, in joules, in the transverse direction shall be:

$$\frac{R_{\text{smys}}}{10}$$

where

$R_{\text{smys}}$  is the specified minimum yield strength, expressed in megapascals.

For steel grade L245, the minimum average Charpy-V absorbed energy in the transverse direction shall be 27 J.

- b) the minimum individual value in any set of tests shall not be less than 75 % of the minimum required average value;
- c) the minimum average and minimum individual values when testing test pieces taken in the longitudinal direction shall be 1,5 times the values stated for transverse test pieces;
- d) if specified (see 9.4.3.2), the shear area shall be an average of 50 % with a minimum individual value of 40 %.

For subsize test pieces, the minimum required absorbed energy values shall be adjusted in accordance with ISO/TR 7705:1991, Clause 6.


## 9.4.4 Through-thickness hardness testing




### 9.4.4.1 Test method

Through-thickness hardness testing shall be performed using the Vickers method in accordance with EN ISO 6507-1, method HV 10 (i.e. with a test force of 98,07 N).

Hardness indent locations for welded fittings shall be in accordance with Figure 3. For seamless fittings, hardness indent locations shall be made at a distance of 1 mm to 2 mm from the inside and outside surfaces containing four indents spaced at 5 mm arranged similarly to Figure 3.

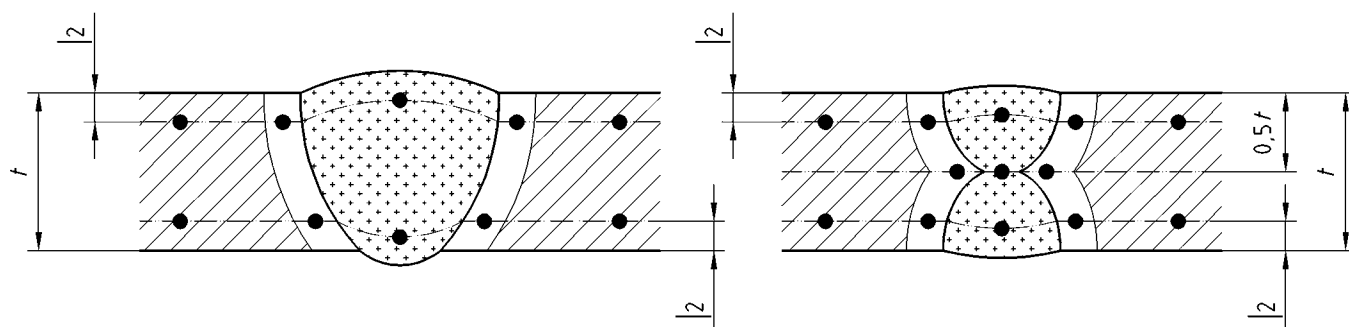Dimensions in millimetres

**Key**

-  Base material
-  Heat-affected zone
-  Weld seam
- $t$  is the thickness

**Figure 3 — Hardness indent locations for welded fittings****9.4.4.2 Acceptance criteria**

No hardness reading shall exceed:

- 300 HV 10 for class A, B and C fittings;
- 250 HV 10 for class CS fittings.

**9.4.5 Surface hardness testing**

The test method and acceptance criteria shall be established by agreement.

**9.4.6 Metallographic examination****9.4.6.1 Test method**

The specimens for through-thickness hardness testing shall be examined, prior to hardness testing, at a magnification of not less than  $\times 100$ . Grain-size measurement shall be performed in accordance with ASTM E 112.

The type of microstructure and actual grain size shall be recorded on the manufacturing procedure qualification test report.

**9.4.6.2 Acceptance criteria**

The minimum average grain size number shall be 7.

**9.4.7 HIC testing**

If HIC testing is specified, the test procedures and acceptance criteria shall be in accordance with EN ISO 15156-2:2003, Annex B.

**9.4.8 SSC testing**

If SSC testing is specified, test procedures and acceptance criteria shall be in accordance with EN ISO 15156-2.

**9.4.9 CTOD testing**

CTOD testing is not required for any fitting class, except by agreement.

Test methods and requirements shall be decided by agreement.

**9.4.10 Guided weld bend testing**

**9.4.10.1 Test pieces**

The test pieces shall be in accordance with EN ISO 7438.

Full-thickness curved-section test pieces are required for fittings with wall thicknesses of 20 mm and above. For fittings with a wall thickness less than 20 mm, the test pieces may be machined to provide a rectangular cross-section with a thickness of 19 mm. The weld reinforcement shall be removed from both faces.

**9.4.10.2 Test method**

The mandrel dimensions shall be as defined in the corresponding part of ISO 3183 for the grade of fitting.

Both test pieces shall be bent through approximately 180°, one with the root of the weld and the other with the face of the weld directly under the mandrel.

**9.4.10.3 Acceptance criteria**

The test pieces shall:

- a) not fracture completely;
- b) not reveal any crack or rupture in the weld metal greater than 3 mm in length, regardless of depth;
- c) not reveal any crack or rupture in the parent metal, heat-affected zone or fusion line longer than 3 mm and deeper than the wall thickness tolerance of the matching pipe.

Cracks that occur at the edges of the specimen and that are less than 6 mm in length shall not be cause for rejection, regardless of their depth.

If a fracture or crack in a test piece is caused by imperfections, the test piece may be discarded and a new test piece substituted.



## 9.5 Non-destructive testing

### 9.5.1 NDT procedures and personnel

All NDT shall be conducted in accordance with documented procedures. If specified by the purchaser, NDT procedures shall be decided by agreement before commencement of fitting manufacture.

All NDT personnel shall be qualified and certified in accordance with ISO 9712 to the appropriate level of competence. The minimum level of competence for UT shall be NDT level 2.

### 9.5.2 Condition of fittings

Except where radiography of the weld seam of the starting material has been specified (see Table 2), all NDT for acceptance of fittings in accordance with the requirements of this document shall be performed after final heat treatment of fittings.

The surface to be examined shall be dry and free of all dirt, grease, lint, scale, welding flux and spatter, oil or other extraneous matter that could interfere with NDT.

Fitting surfaces shall be finished so that surface imperfections can be detected by visual inspection.

### 9.5.3 Treatment of imperfections

#### 9.5.3.1 Defects

Fittings shall be free of the following defects:

- a) dents with sharp-bottom gouges;
- b) dents, without sharp-bottom gouges, exceeding 3 mm in depth;
- c) peaks exceeding 3 mm in height;
- d) hard spots;
- e) weld reinforcement exceeding 3 mm, for fittings with a wall thickness of 12 mm or less;
- f) weld reinforcement exceeding 4 mm for fittings with a wall thickness greater than 12 mm;
- g) incompletely-filled weld preparations;
- h) radial offset of plate edges, or plate misalignment, exceeding 2 mm, for fittings with a wall thickness of 12 mm or less;
- i) radial offset of plate edges, or plate misalignment, exceeding 3 mm, for fittings with a wall thickness greater than 12 mm;
- j) laps, flats, tears, pulls and similar defects.

NOTE Definitions and visual examples of some of these imperfections can be found in ASM International's Metals Handbook.

#### 9.5.3.2 Treatment of surface imperfections

Imperfections not classified as defects may remain in the fitting without repair. Localized grinding, however, may be performed.

### **9.5.3.3 Treatment of dressable surface defects**

All dressable surface defects shall be dressed out by grinding. Grinding shall be carried out in such a way that the dressed area blends in smoothly with the contour of the pipe. Complete removal of defects shall be verified by local visual inspection, aided if necessary by suitable NDT methods. After grinding, the remaining wall thickness in the dressed area shall be checked for compliance with 9.6.

### **9.5.3.4 Treatment of non-dressable surface defects**

Fittings containing non-dressable defects shall be given one of the following dispositions:

- weld defects in welded fittings shall be repaired in accordance with 9.5.3.5;
- the fitting shall be rejected.

### **9.5.3.5 Repair of defects by welding**

Repair by welding on weld seams may be performed only by the following processes:

- submerged arc welding;
- manual metal-arc welding;
- metal inert gas/metal active gas welding;
- tungsten inert gas welding.

Weld defects separated by less than 100 mm shall be repaired as a continuous single weld repair.

Each single repair shall be carried out with a minimum of two weld passes over a minimum length of 50 mm.

The weld repair work shall be performed using procedures qualified in accordance with 8.3.2.

After weld repair, the total area of the repaired zone shall be subjected to RT in accordance with 9.5.5.

### **9.5.4 Fitting ends**

The complete end preparation shall be subjected to MT in accordance with ISO 13664, or PT in accordance with ISO 12095. The MT technique should employ fluorescent ink.

For MT and PT, linear indications with a length less than 2 mm shall be acceptable.

For class B and C fittings, a 50 mm wide band at each end shall be inspected for laminar imperfections by UT in accordance with ISO 11496. This 50 mm band shall extend from the intersection of the weld bevel and fitting outside diameter back along the body of the fitting. Laminar imperfections shall not exceed a length of 6 mm in the circumferential direction and their area shall not exceed 100 mm<sup>2</sup>.

### **9.5.5 Weld seams**

Weld seams shall be subjected to RT in accordance with ISO 12096. The image quality class shall be R1. The acceptance criteria shall be in accordance with ISO 12096. Instead of radiographic examination, ultrasonic examination may be substituted by agreement.

### **9.5.6 Guide bar attachment welds**

Guide bar attachment welds shall be subjected to MT in accordance with ASTM E 709.

### 9.5.7 Fitting body

If specified, the methods and acceptance criteria for fitting body NDT shall be decided by agreement prior to fitting manufacture.

### 9.5.8 Residual magnetism

The residual magnetic flux density at the fitting ends shall not exceed 3 mT.

## 9.6 Dimensions

Dimensions and tolerances shall be in accordance with MSS SP-75 and, for nominal sizes less than DN 400, ASME B16.9.

### 9.7 Gauging

The requirements for gauging, including pigging assessments, shall be decided by agreement.

### 9.8 Hydrostatic testing

Hydrostatic testing of fittings may be omitted, unless otherwise specified. If hydrostatic testing is omitted, the manufacturer shall certify that the fitting will withstand an internal pressure at least as high as that specified for the mating pipe.

## 10 Inspection document

The required ISO 10474 designation of inspection document, and any specific requirements for format and content of the document, shall be specified.

## 11 Marking

One or both ends of each fitting shall be marked with the following information:

- purchase order and item number;
- fitting designation, as defined in Clause 5;
- nominal wall thickness at the fitting ends;
- dimensions;
- heat number or manufacturer's heat identification;
- manufacturer's name or trademark;
- any additional marking specified in the purchase order.

For fittings designed with a lower SMYS than the matching pipe, both the fitting designation and the intended matching pipe grade shall be marked.

Markings shall be made with indelible paint on the inside surface or, if it is not possible to mark on the inside surface (i.e. for smaller diameter fittings), on the outside.

## **EN 14870-2:2004 (E)**

For fittings of DN 100 and larger, markings shall be executed in block capitals of minimum height of 19 mm. For smaller fittings, the character height shall be appropriate. Identification markings shall not be applied on weld bevels.

In addition to paint-marking, the manufacturer's unique fitting identification number shall be die-stamped on a weld bevel of each fitting.

## Annex A (normative)

### Design calculations

#### A.1 Elbows

The minimum wall thickness of the extrados shall be equal to  $t$ .

The wall thickness of the intrados shall be determined from the following formula:

$$t_i = t \times E$$

where

$t_i$  is the minimum wall thickness required in the elbow intrados;

$E$  is a factor given in Table A.1.

**Table A.1 —  $E$ -values for intrados wall thickness calculation**

$R/D^a$	$E$
1 <sup>b</sup>	1,25
1,5 <sup>c</sup>	1,1
3	1,04
Intermediate values may be interpolated.	
<sup>a</sup> Elbow centreline radius divided by outside diameter. <sup>b</sup> Known as a short-radius elbow. <sup>c</sup> Known as a long-radius elbow.	

#### A.2 Caps

Caps shall be ellipsoidal in shape with base radius to depth ratio of 2:1. Approximation of ellipsoidal shape by spherical radii (head  $0,9 \times$  base diameter and knuckle  $0,17 \times$  base diameter) may be performed. A straight skirt length shall be included in the cap. The minimum wall thickness within the body of the cap, the knuckle, and the straight skirt shall be equal to  $t$ .

### A.3 Reducers (eccentric or concentric)

#### A.3.1 Reducers with tangents

Reducers shall consist of a reduction section which is essentially conical, tangents at each end, and knuckle radii joining the conical section to the tangents. The following rules shall apply to the reducer design:

- a) the cone angle shall not exceed 30°;
- b) the larger of  $D_L/t_{D_L}$  and  $D_n/t_n$  shall not exceed 100:

where

$D_L$  is the outside diameter of the larger end of the reducer;

$t_{D_L}$  is the nominal wall thickness of the larger end of the reducer;

$D_n$  is the outside diameter at the point,  $n$ , under consideration, measured perpendicular to the longitudinal axis;

$t_n$  is the wall thickness at diameter  $D_n$ .

- c) the minimum wall thickness shall be not less than  $t$  throughout the body of the reducer, except in and immediately adjacent to the cylinder portion of the small end, where the minimum thickness shall be not less than  $t_1$ .

#### A.3.2 Conical reducers

The included (apex) angle,  $\alpha$ , of a concentric reducer shall not exceed 60°.

The included angle,  $\alpha$ , of an eccentric reducer shall not exceed 30°.

The minimum thickness,  $t_{\min}$ , of the conical shell section shall be determined by the following equation.

$$t_{\min} = \frac{pD_1}{2 \cos \alpha [R_{m,\text{red}} - (0,6 p)]}$$

where

$p$  is the design pressure;

$D_1$  is the outside diameter at the point under consideration, measured perpendicular to the longitudinal axis;

$\alpha$  is the included (apex) angle;

$R_{m,\text{red}}$  is the allowable tensile strength of the reducer.

#### A.4 Tees (full outlet and reducing)

Outlets of tees shall be integral with the bodies. Tees with separately welded outlets shall not be supplied. The radius of curvature of the external contoured portion of the outlet,  $\rho_o$ , shall not be less than  $0,05 D$  (except that on branch sizes larger than DN 760,  $\rho_o$  need not exceed 30 mm), nor shall it be larger than  $[(0,10 \times D) + 12]$  mm. Machining shall not be employed in order to meet the above requirements concerning  $\rho_o$ . The minimum crotch thickness of the tee at the  $45^\circ$  plane shall be  $(1,5 \times t)$ .

## Annex B (normative)

### Proof test

#### B.1 Preparation for testing

Fittings consistent with those of the products manufactured shall be selected as the test specimens. The fittings shall be inspected for compliance with the dimensional requirements of 9.6. Straight seamless or welded pipe which matches the wall designation intended to be used with the fitting in service shall be connected to the test specimen in a way that represents the intended service conditions. The matching pipe and tested fittings shall also be representative of the material to be used in service.

The length of matching pipe connected to the test specimen should be at least equal to the matching pipe nominal diameter. For a branch fitting to a header, the length of matching pipe shall be measured from the edge of the fitting. Beyond the one-diameter minimum length, the matching pipe may be capped or reinforced so the pipe will not fail prematurely. The test may be based on pressure only if the design load condition is limited to pressure, i.e. if there are no pipe forces on the fitting exceeding the end-cap force.

#### B.2 Test pressure

The required test pressure shall be calculated using the following equation:

$$p_p = \frac{2f R_m t_p}{D_p}$$

where

- $p_p$  is the numerical value of the computed proof pressure, expressed in megapascals;
- $f$  is the testing factor determined from Table B.1, dimensionless;
- $R_m$  is the tensile strength of the test fitting, expressed in megapascals;
- $t_p$  is the nominal wall thickness of the matching pipe, expressed in metres;
- $D_p$  is the specified outside diameter of the matching pipe, expressed in metres.

Additionally, tests in various sizes within the manufacturing capability shall be performed to help develop design formulae or criteria to be used in the design of sizes not subjected to testing.

A minimum of three tests should be considered.



Table B.1 — Testing factors

Number of tests	Testing factor <i>f</i>
1	1,10
2	1,05
3	1

### B.3 Test method and equipment

The pressurizing medium shall be water or other suitable liquid. The test pump shall have a pressure-delivering capacity greater than 1,25 times the computed proof pressure determined from B.2. The pressure-measuring device shall be a dial-indicating type or a pressure-transducer type, with a range of pressure measurement that shall not be less than 1,5 times, nor more than 4 times, the computed or specified proof pressure. Dial-indicator graduations shall be such that accurate readings of the pressure measuring device can be made and readings shall not produce errors greater than 5 % of the actual proof pressure. The pressure-measuring device shall have been calibrated within six months of the test and shall be visible to the pump operator throughout the test.

The pressurization of the test assembly shall be in a gradual and incremental manner, not exceeding a rate of 2,75 MPa/min, until the assembly fails by loss of pressure integrity or until a pressure of 1,05 times the computed test pressure is exceeded.

### B.4 Establishment of the equivalent wall or schedule

A pipe fitting configuration shall be considered adequate when the actual proof pressure achieved during the test is at least equal to the computed proof pressure. The fitting or joint shall then be considered to have an equivalent weight designation or schedule number to the matching pipe.

### B.5 Applicability of results

A pressure rating for one pipe fitting may represent other pipe fittings to the extent permitted in this document.

Tests for single or replicate specimens may be extrapolated to qualify geometrically-similar specimens no smaller than half, nor larger than twice, the size of the test specimen. The similarity of untested specimens shall be judged by comparison of attributes which relate to the failure mode of the specimen, such as  $D_p/t$  (pipe outside diameter divided by nominal wall thickness) or cross-sectional area.

The results of testing DN 600 pipe may be extrapolated to any larger size pipe if DN 600 is the largest pipe size possible in the proof test assembly.

The satisfactory test of a non-reducing fitting qualifies reducing fittings of the same pattern and method of manufacture.

The satisfactory test of an elbow qualifies elbows having a greater centreline radius than the test fitting, provided they meet the size and attributes requirements stated above.

## **B.6 Test report**

A report of the test shall be prepared and shall include the following information:

- a) a description of the test;
- b) the instrumentation and methods of calibration used;
- c) the actual proof pressures for each test;
- d) the time period from test initiation to failure point;
- e) the calculations performed;
- f) a description of the failure mode, or modes, and a sketch or picture of the failure;
- g) the basis for any extrapolation to similar pipe fittings;
- h) the equivalent pipe wall or schedule rating.

## **B.7 Maintenance of results**

The manufacturer shall have a quality control program that verifies the manufacturing processes used and assures that the resulting geometries of the fittings manufactured are consistent with the geometries tested. The quality control program shall control the manufacturing drawings and maintain records showing conformance to these drawings.

Whenever a significant change is made in the geometry or method of manufacture, the manufacturer shall either retest a representative sample of the new production or show by analysis that the change would not alter the results of the prior test.

## Annex ZA (normative)

### Normative references to international publications with their corresponding European publications

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies

NOTE Where an International Publication has been modified by common modifications, indicated by (mod.), the relevant EN/HD applies.

Publication	Year	Title	EN	Year
ISO 377	1997	<i>Steel and steel products — Location and preparation of samples and test pieces for mechanical testing.</i>	EN ISO 377	1997
ISO 2566-1	1984	<i>Steel — Conversion of elongation values — Part 1: Carbon and low alloy steels.</i>	EN ISO 2566-1	1999
ISO 6507-1	1997	<i>Metallic materials — Vickers hardness test — Part 1: Test method.</i>	EN ISO 6507-1	1997
ISO 7438	1985	<i>Metallic materials — Bend test.</i>	EN ISO 7438	2000
ISO 13623	2000	<i>Petroleum and natural gas industries — Pipeline transportation systems (ISO 13623:2000 modified).</i>	EN 14161	2003

## Bibliography

- [1] EN ISO 8501-1, *Preparation of steel substrates before application of paints and related products — Visual assessment of surface cleanliness — Part 1: Rust grades and preparation grades of uncoated steel substrates and of steel substrates after overall removal of previous coatings.*
- [2] ISO 3545-3, *Steel tubes and fittings — Symbols for use in specifications — Part 3: Tubular fittings with circular cross-section.*
- [3] ASM International<sup>4)</sup>, *Metals Handbook*, Eighth Edition, Volume 11, 1976, pp 287-329.

---

4) American Society for Metals, ASM International, 9639 Kinsman Road, Materials Park, OH 44073-0002, USA.



---

---

## BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

### Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.  
Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

### Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001.  
Fax: +44 (0)20 8996 7001. Email: [orders@bsi-global.com](mailto:orders@bsi-global.com). Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

### Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.  
Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: [info@bsi-global.com](mailto:info@bsi-global.com).

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.  
Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001.  
Email: [membership@bsi-global.com](mailto:membership@bsi-global.com).

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

### Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager.  
Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553.  
Email: [copyright@bsi-global.com](mailto:copyright@bsi-global.com).